

A Model to Simulate Cathodic Protection of Steel by Thermally Sprayed Aluminium in Presence of Defect



UNIVERSITY OF
LEICESTER

Adriana Castro Vargas^{1,2}, Simon Gill¹ and Shiladitya Paul^{1,3}

1. School of Engineering, University of Leicester, University of Road, Leicester LE1 7RH, UK

2. NSIRC, TWI Ltd, Granta Park, Great Abington, Cambridge, CB21 6AL, UK

3. Materials and Structural Integrity Technology Group, TWI, Granta Park, Cambridge CB21 6AL, UK



Lloyd's Register
Foundation



Motivation

Thermal spray aluminium (TSA) coatings have been reported to provide cathodic protection of steel structures under immersed conditions in marine environments. However, the level of damage these coatings can tolerate is not fully explored. Simulations using COMSOL Multiphysics®, were conducted to understand the behaviour of sacrificial aluminium coatings obtained by arc spray with varying areas of damage and its capacity to polarise steel in artificial seawater.

Model System

Reactions

When TSA - coated steel with defect is exposed to seawater, the oxygen reduction reaction happens on steel surface, while anodic reaction happens on the coating[1].

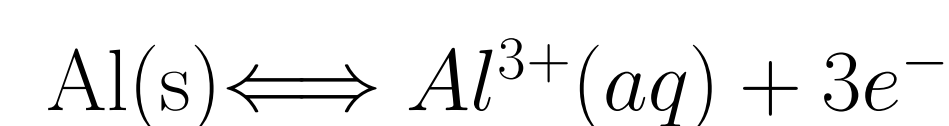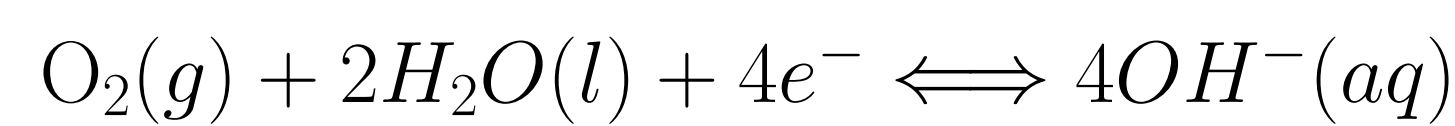

Geometry

Experiment A. Electrochemical behaviour of AA 1050 coating with damage in artificial seawater[2].

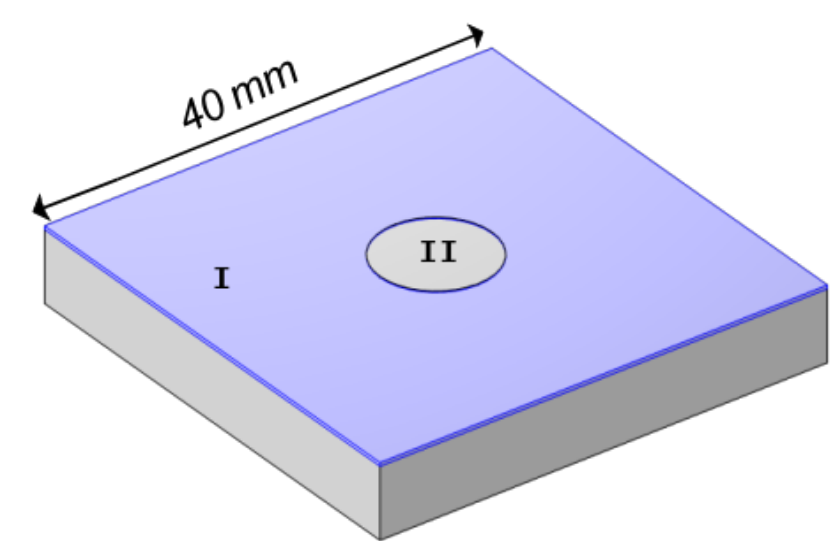


Figure 1: Thermally sprayed coated sample with 5 % of surface area defect. (I) TSA coating. (II) Steel exposed.

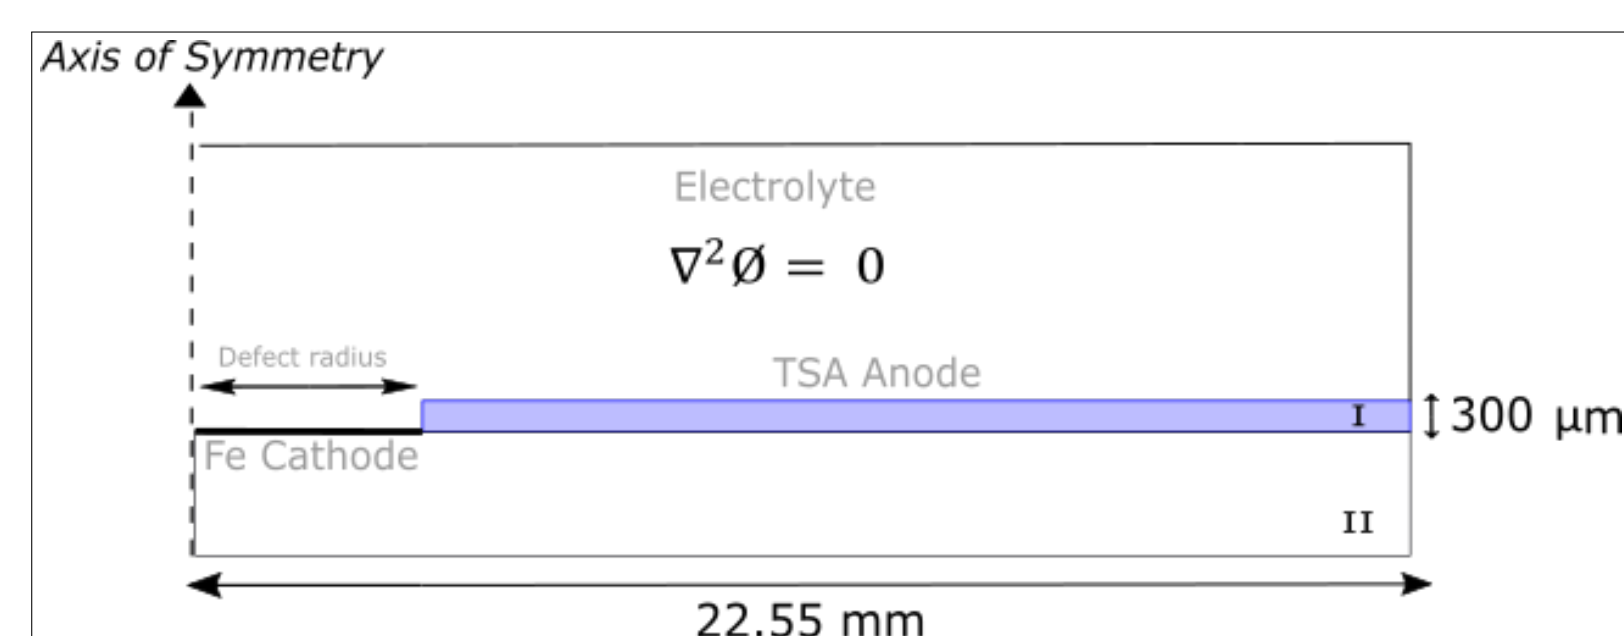


Figure 2: Geometry of the model. 2D axi-symmetric space dimension.

Experiment B. Testing of AA 1050 coating in artificial seawater with extreme damage[3].

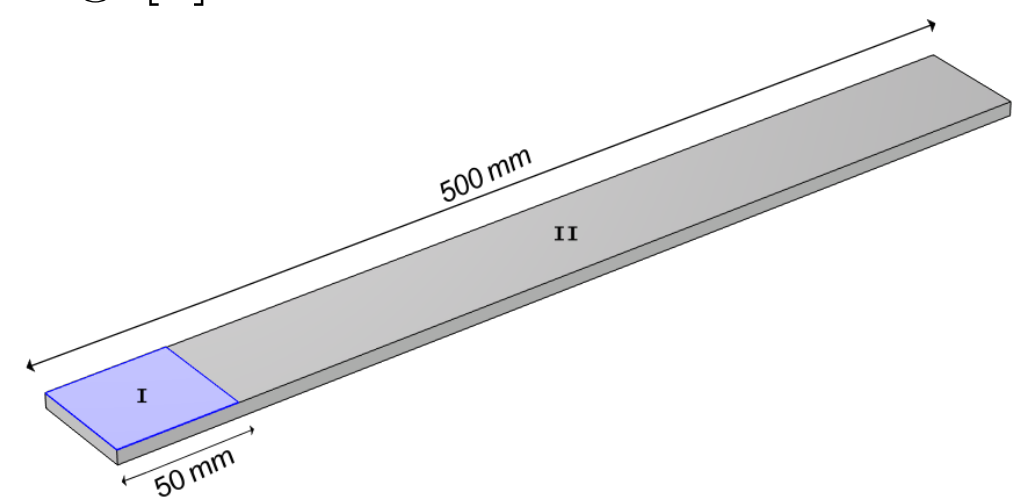


Figure 3: Thermally sprayed coated sample with 90 % of surface area defect. (I) TSA coating. (II) Steel exposed.

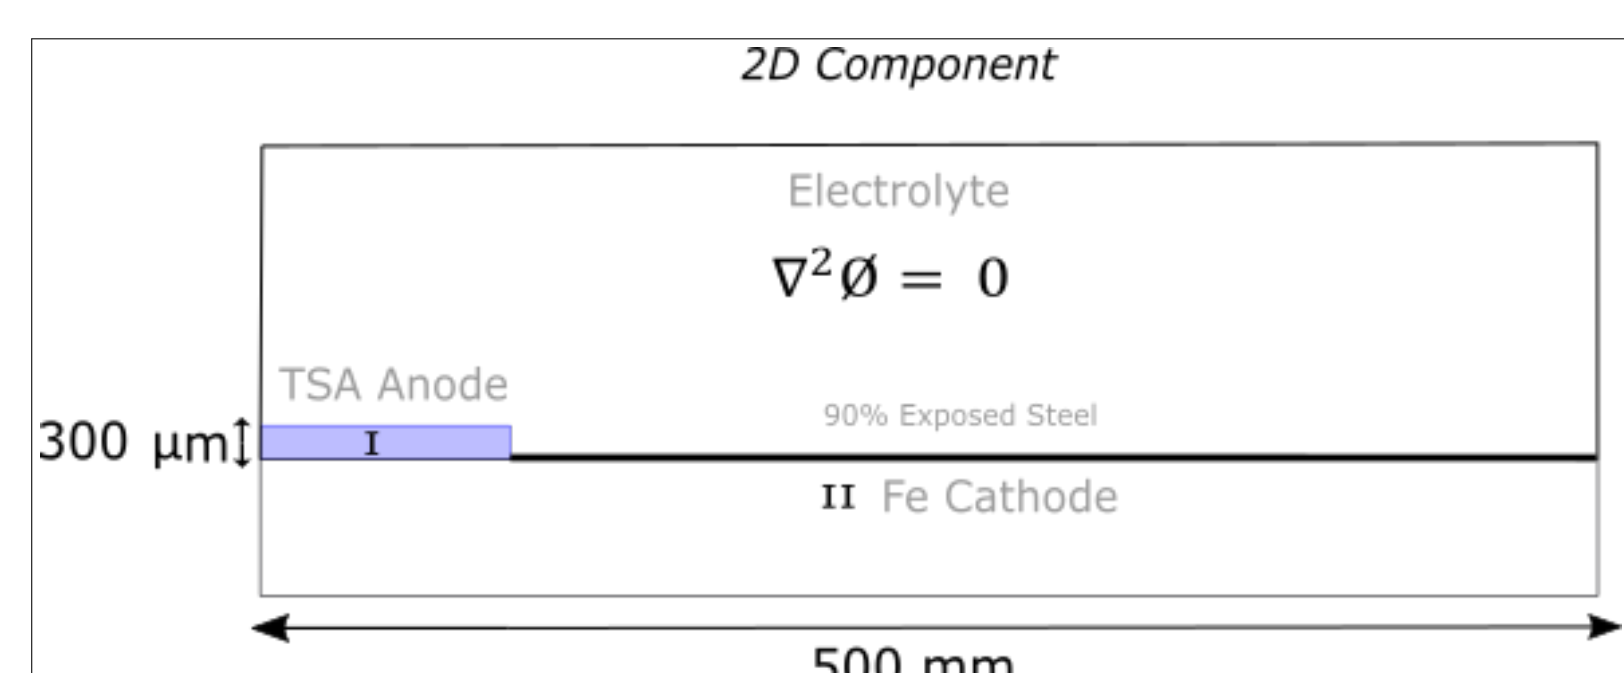


Figure 4: Geometry of the model. 2D space dimension.

Boundary Conditions

Governing Equations

Transport of species is represented by Nernst-Planck equation

$$N_i = -D_i \nabla c_i - z_i F u_i c_i \nabla \phi + c_i v \quad (1)$$

Steady-state electrolyte, the solution velocity v is zero

$$\frac{\partial c_i}{\partial t} = -\nabla \cdot N_i = 0 \quad (2)$$

Electrolyte is assumed electroneutral

$$\sum_i^n z_i c_i = 0 \quad (3)$$

The cathode is assumed to be not corroding

$$\nabla^2 \phi = 0 \quad (4)$$

Ohm's law is applied to calculate potential gradient on the anode boundary

$$\nabla \phi = -\frac{j_a}{\sigma} \quad (5)$$

where j_a is the local current density and σ is the electrolyte conductivity[4].

Parameters

Parameter	Value	Source
E_{corr} Steel	-0.68 V	[3]
E_{corr} AA1050	-0.98 V	[1, 2]
j_{corr}	$5.5 \times 10^{-2} \frac{A}{m^2}$	[1]
α_a	0.57 V/dec	[1]
α_c	0.18 V/dec	[1]
σ	5 S/m	

Table 1: Mixed potentials are referred to Ag/AgCl (Sat.KCl) electrode.

Time - Dependent Modelling

Arbitrary Lagrangian Eulerian (ALE) was used as a moving mesh technique to simulate the consumption of the TSA coating surface[4]. Corrosion products and deposit layers are not taken into account in the model.

$$n.v = \frac{M j_{corr}}{z F \rho} = \frac{M j_a}{z F \rho} \quad (6)$$

Results

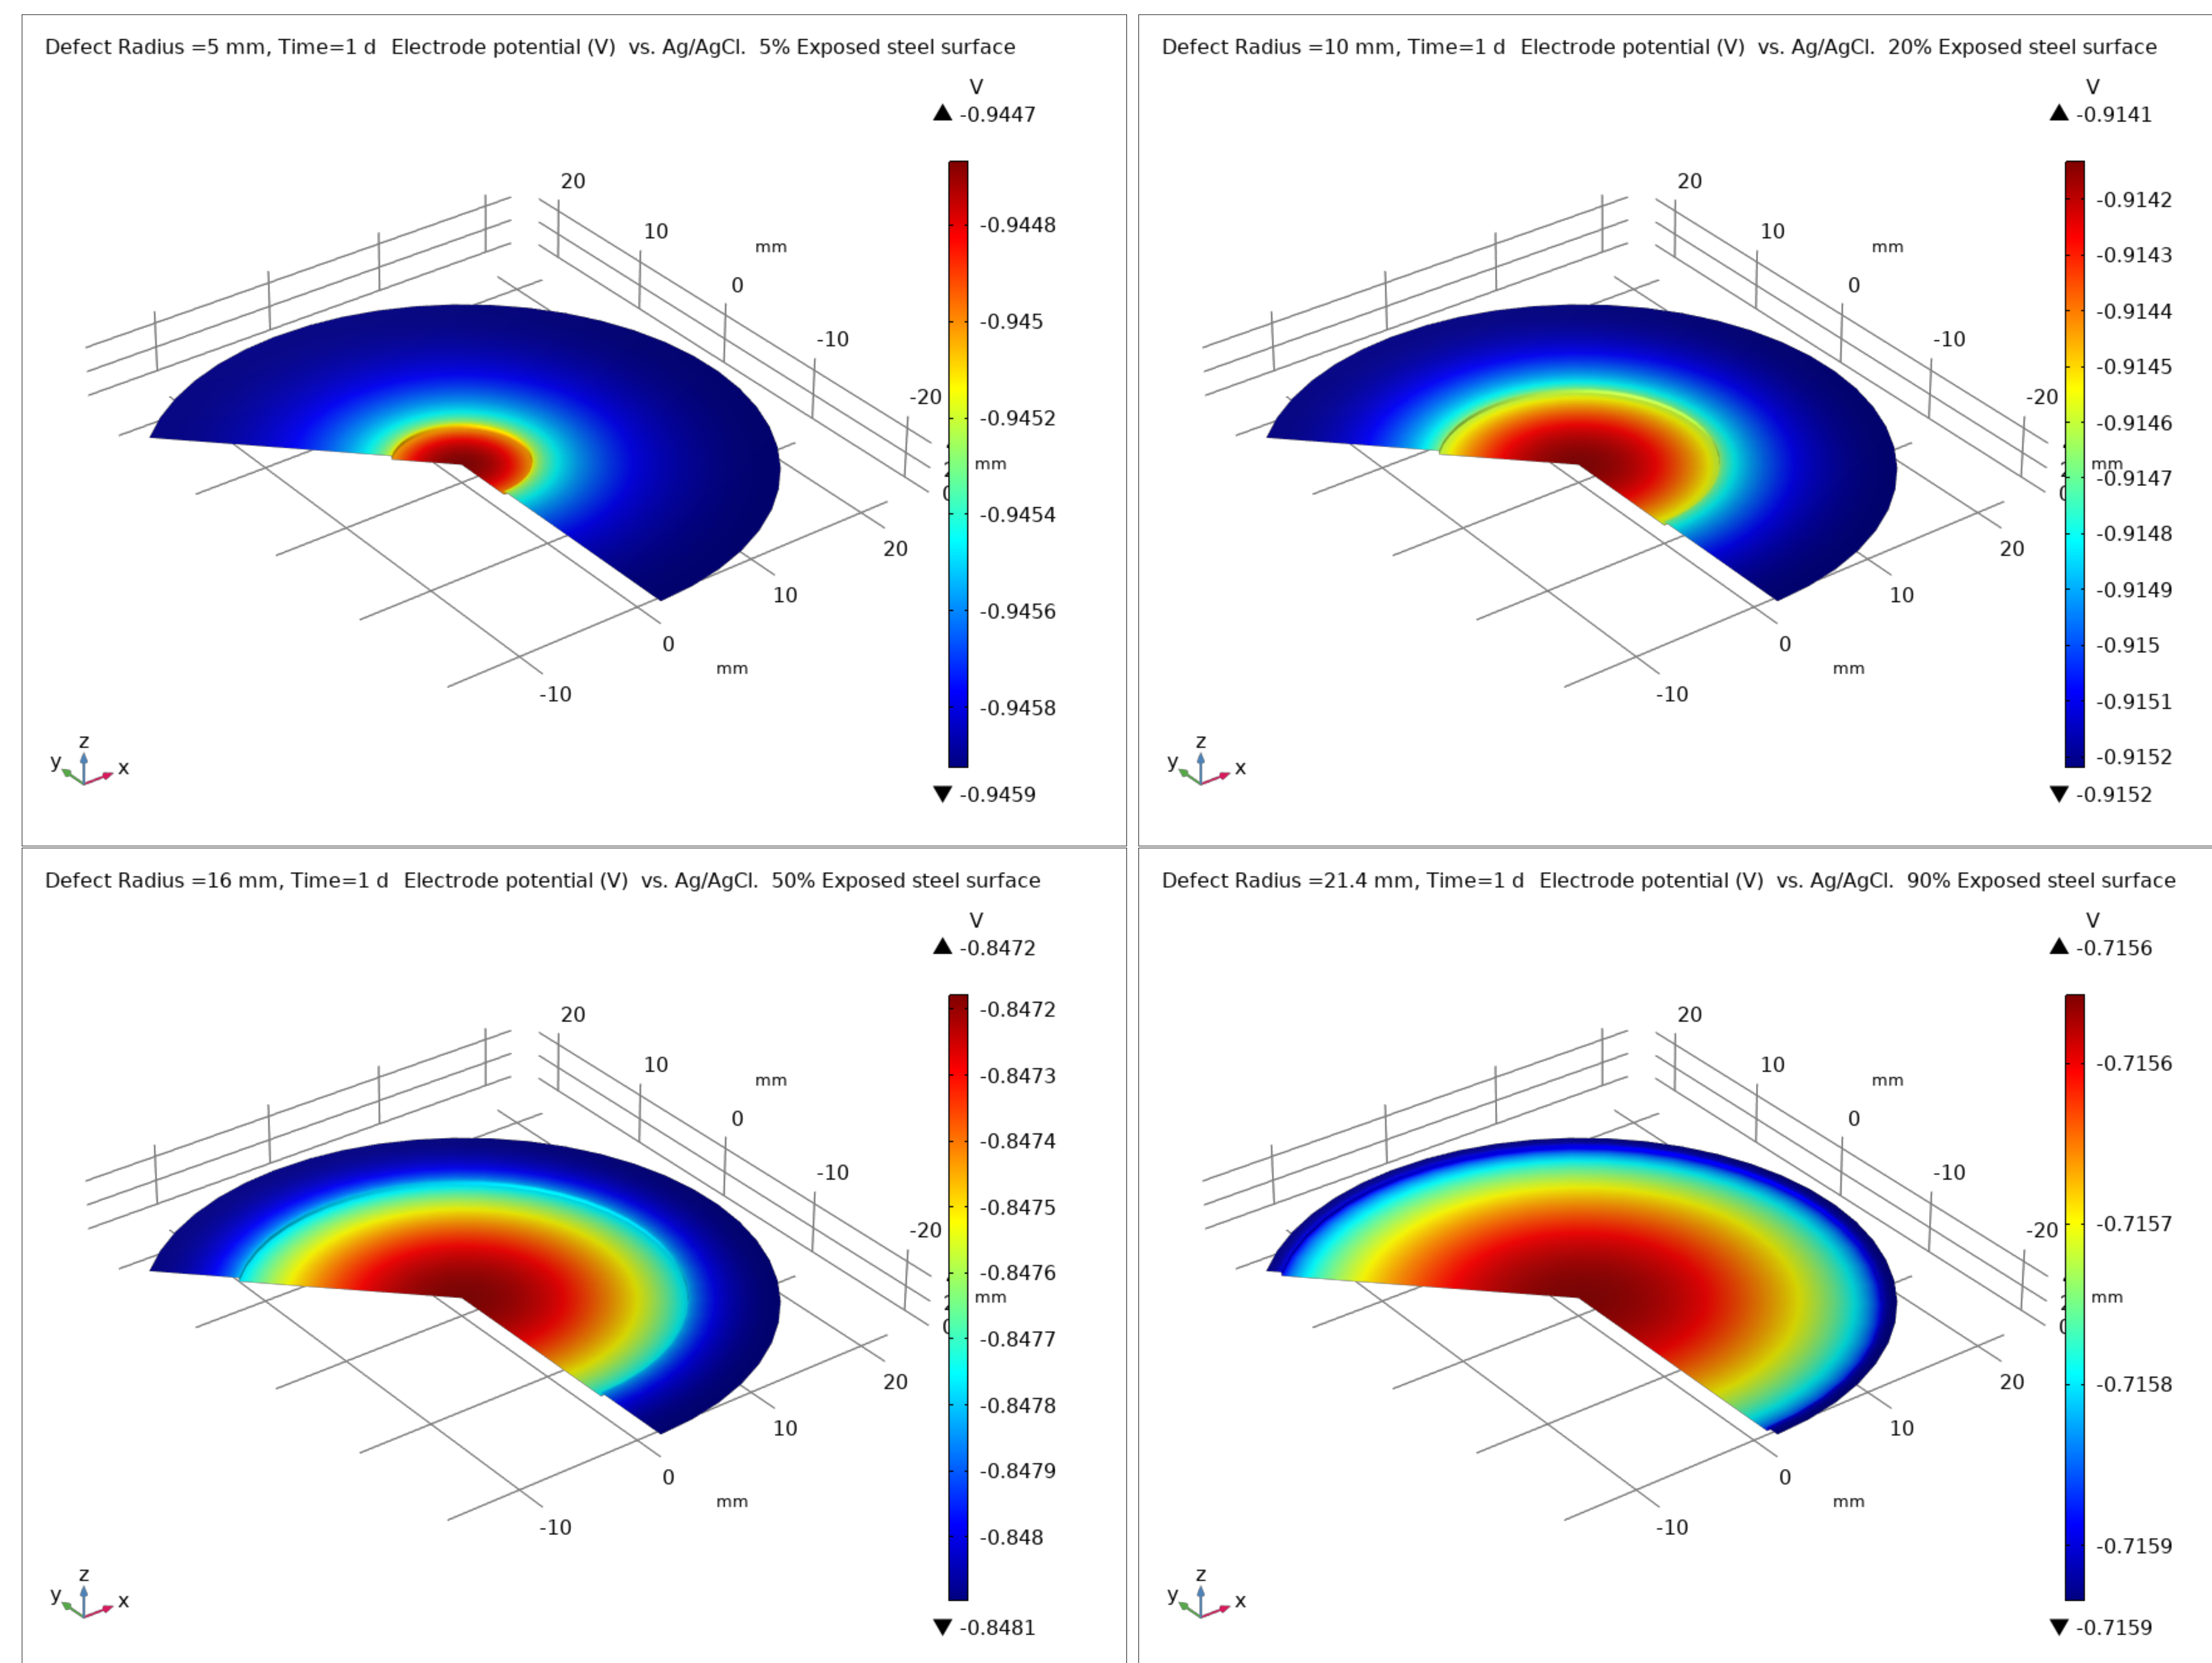


Figure 5: Sacrificial protection offered by thermal spray aluminium coating as a function of the exposed steel surface area.

Comparison With Experiments

Experiment A. Open circuit potential (OCP) within 50 days.

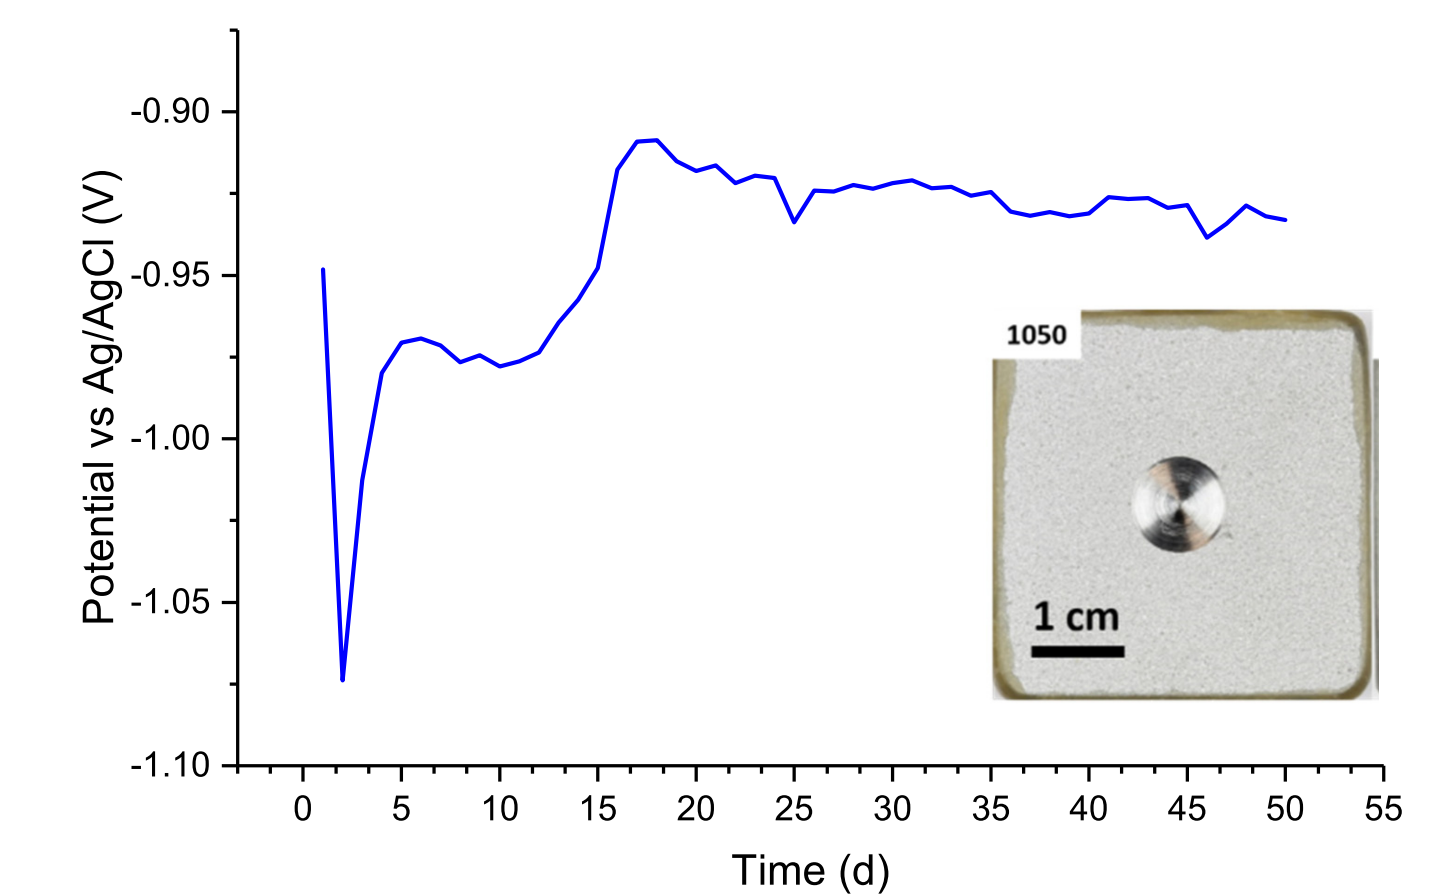


Figure 6: OCP of thermally sprayed coated sample with 5 % of surface area defect[1, 2].

Experiment B. $C_{R,Exp} = 0.42 \frac{mm}{y}$ [3] and $C_{R,Model} = 0.38 \frac{mm}{y}$ within 7 days.

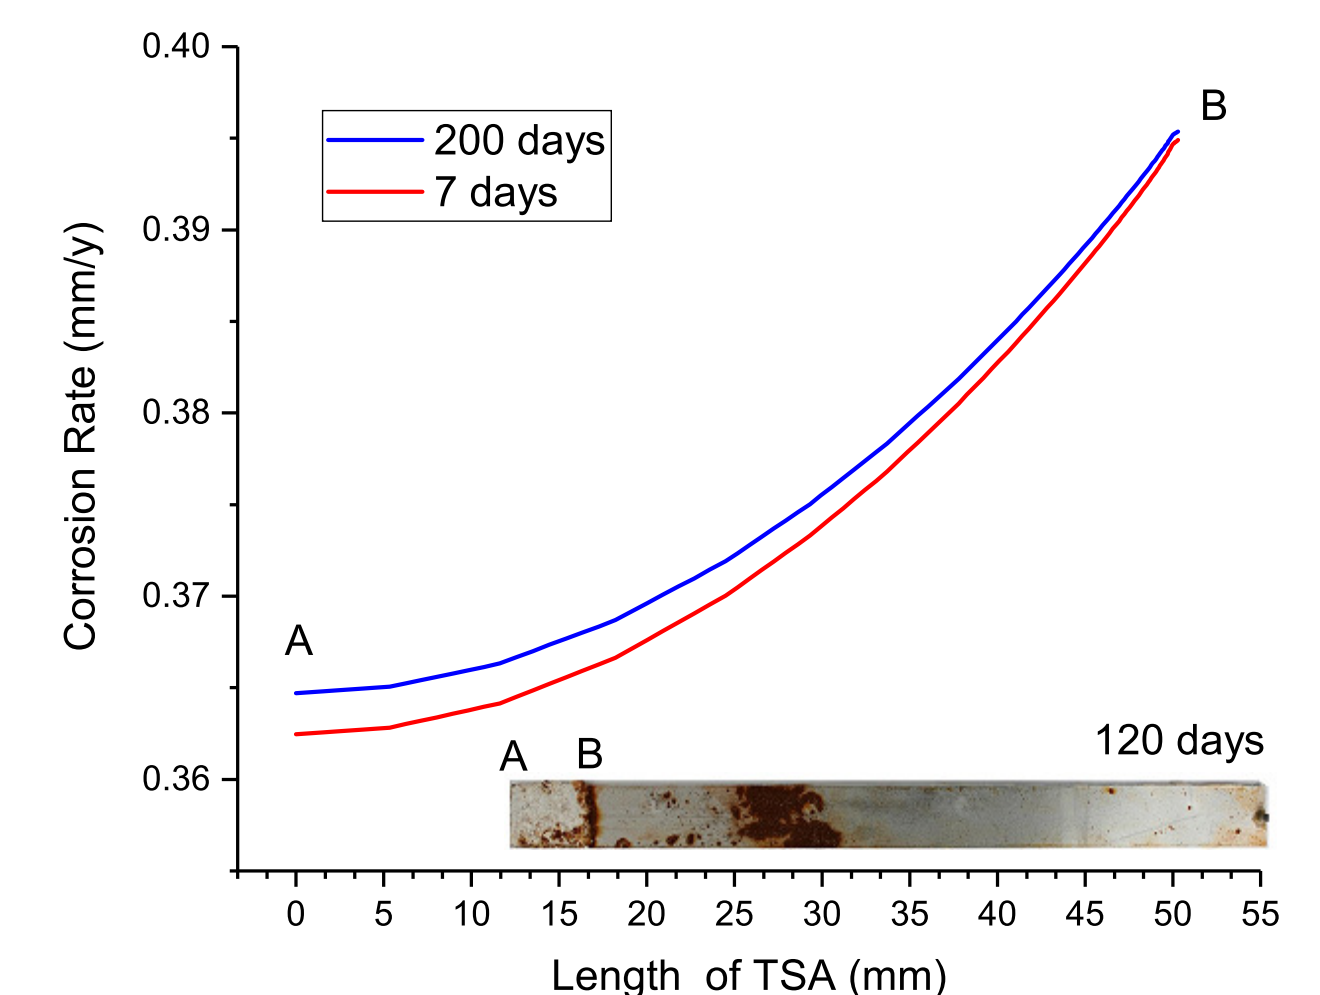


Figure 7: Simulated corrosion rates (C_R).

Conclusion and Future Work

The corrosion rates and sacrificial protection obtained using the model are in broad agreement with those estimated from laboratory experiments. Future time-dependent simulations need to integrate corrosion products and deposit layers.

Acknowledgements

This publication was made possible by the sponsorship and support of Lloyd's Register Foundation. Lloyd's Register Foundation helps to protect life and property by supporting engineering-related education, public engagement and the application of research. The work was enabled through, and undertaken at, the National Structural Integrity Research Centre (NSIRC), a postgraduate engineering facility for industry-led research into structural integrity established and managed by TWI through a network of both national and international Universities. The authors gratefully acknowledge the Colombian Ministry of Science, Technology, and Innovation (MinCiencias) for the financial support of Adriana Castro Vargas. Scholarship program No. 860 - 2019.

References

- [1] R. Grinon-Echaniz, S. Paul, R. Thornton, P. Refait, M. Jeannin, and A. Rodriguez, "Prediction of thermal spray coatings performance in marine environments by combination of laboratory and field tests," *Coatings*, vol. 11, no. 3, p. 320, 2021.
- [2] R. Grinon-Echaniz, P. Refait, M. Jeannin, R. Sabot, S. Paul, and R. Thornton, "Study of cathodic reactions in defects of thermal spray aluminium coatings on steel in artificial seawater," *Corrosion Science*, vol. 187, p. 109514, 2021.
- [3] S. Paul, "Cathodic protection of offshore structures by extreme damage tolerant sacrificial coatings," in *NACE International Corrosion Conference Proceedings*, pp. 1-12, NACE International.
- [4] M. Saeedikhani, S. Wijesinghe, and D. J. Blackwood, "Moving boundary simulation and mechanistic studies of the electrochemical corrosion protection by a damaged zinc coating," *Corrosion Science*, vol. 163, p. 108296, 2020.

Downloads

ALE Animation



acv6@leicester.ac.uk

Poster

